



**Federal Aviation
Administration**

International Aircraft Materials Fire Test Working Group Meeting

Development of New Flammability Tests for Magnesium-Alloy Cabin Components

Presented to: International Aircraft Materials Fire Test
Working Group, Mobile, AL

By: Tim Marker, FAA Technical Center


Date: March 7-8, 2017



Development of Flammability Test for Magnesium Components Located in Inaccessible Areas (Update)



3- by 6-inch Thin Magnesium Sample

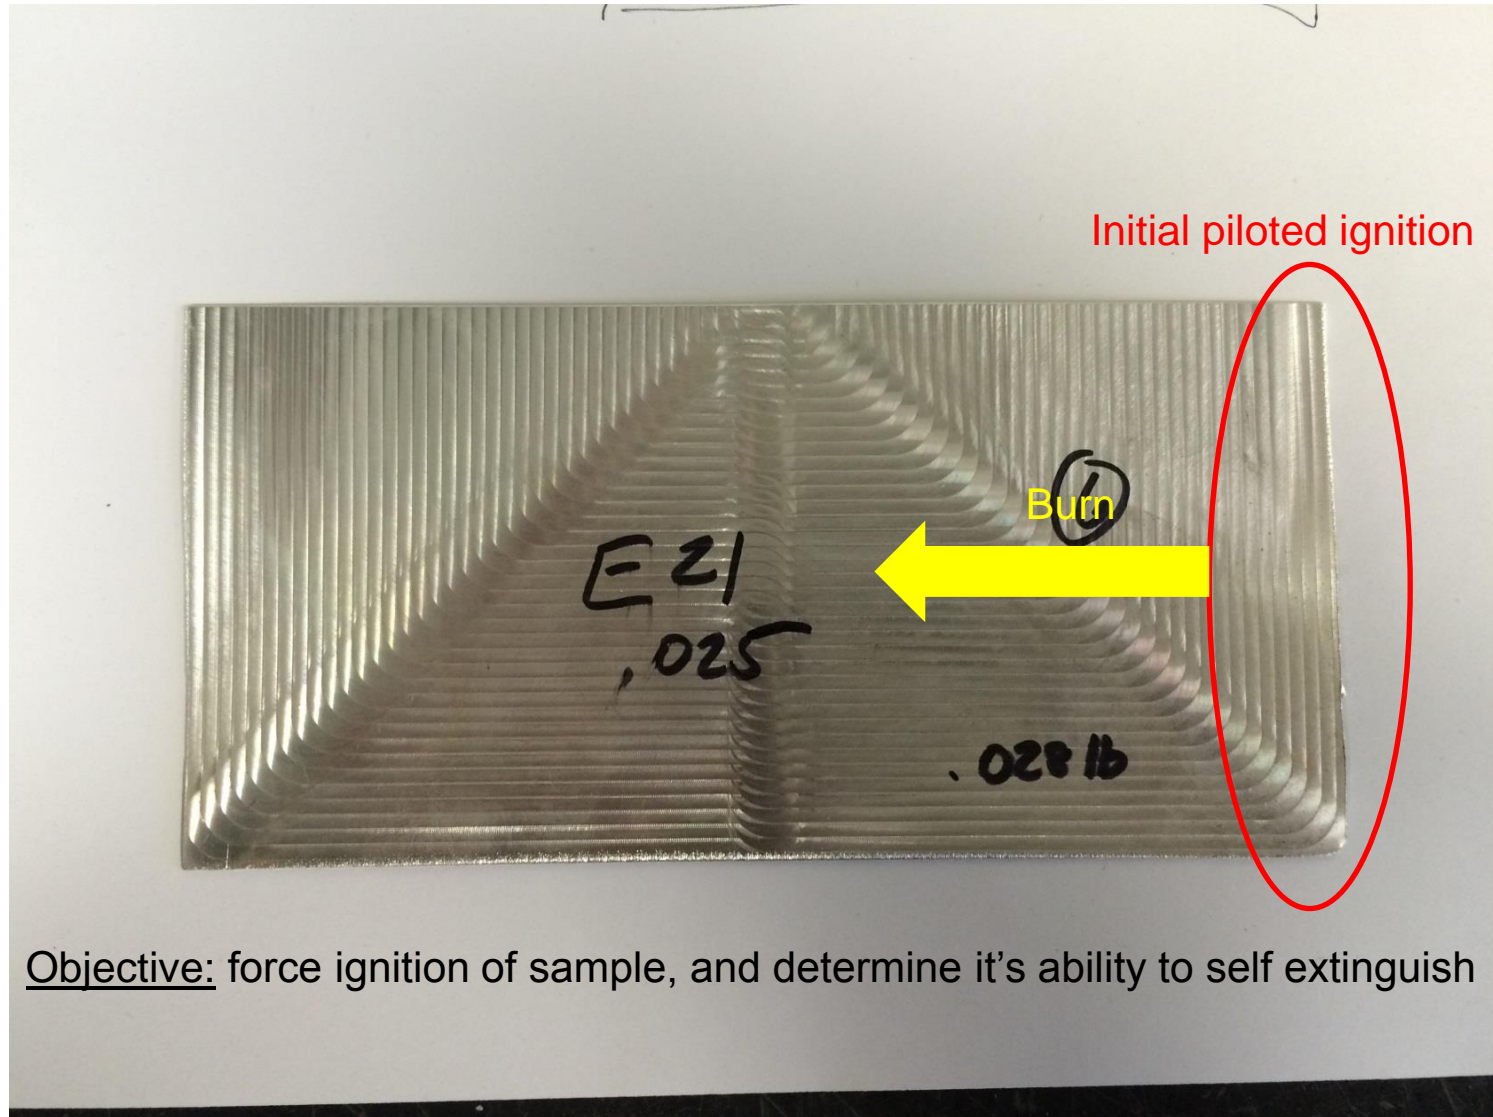


Objective: force ignition of sample, and determine it's ability to self extinguish


Development of Flammability Test for Magnesium Components Located in Inaccessible Areas (Update)

- *125 tests completed using radiant panel apparatus*
- *3- by 6-inch sample size*
- *2-minute piloted ignition, 4-minute total exposure*
- *0.025-inch and 0.050-inch thickness samples tested*
- *Various shapes and sizes of sample holders tested*

0.025-Inch Thickness (2-Minute Pilot, 4-Minute Exposure, 78 Tests)

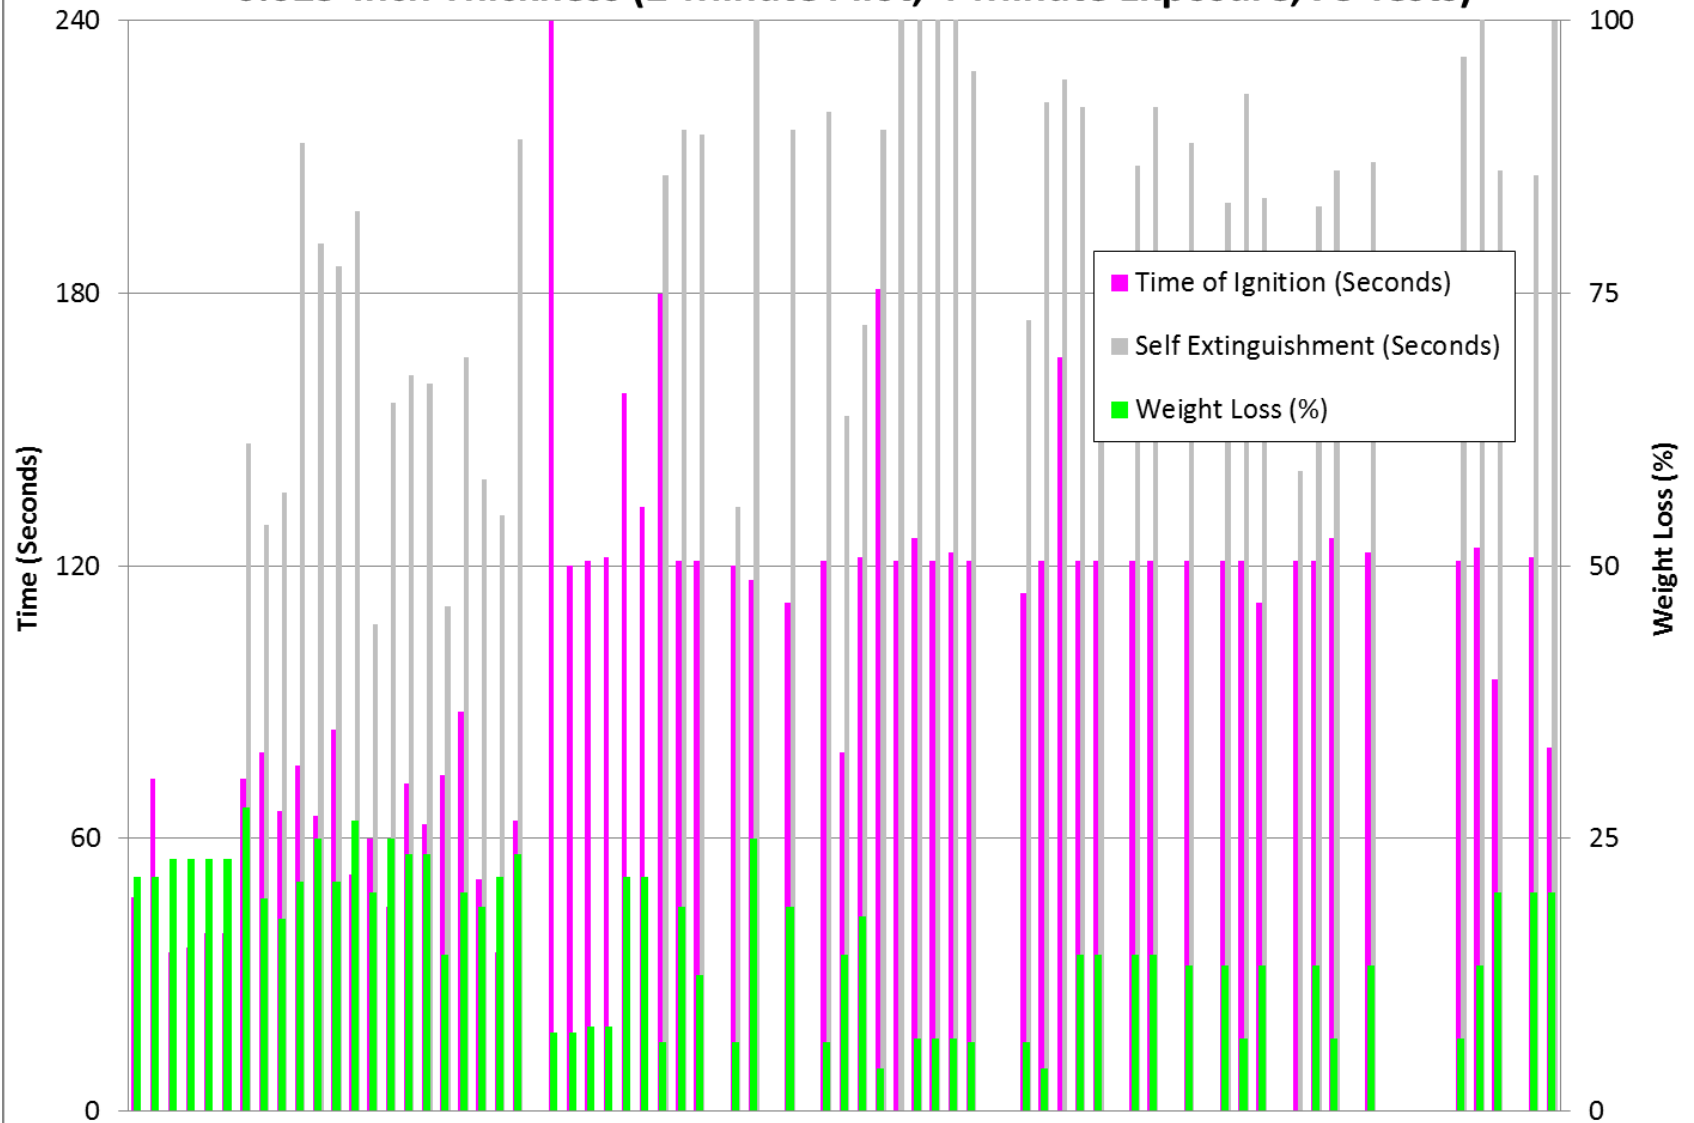

0.025-Inch Thickness Sample Weight Loss (%), 78 Tests

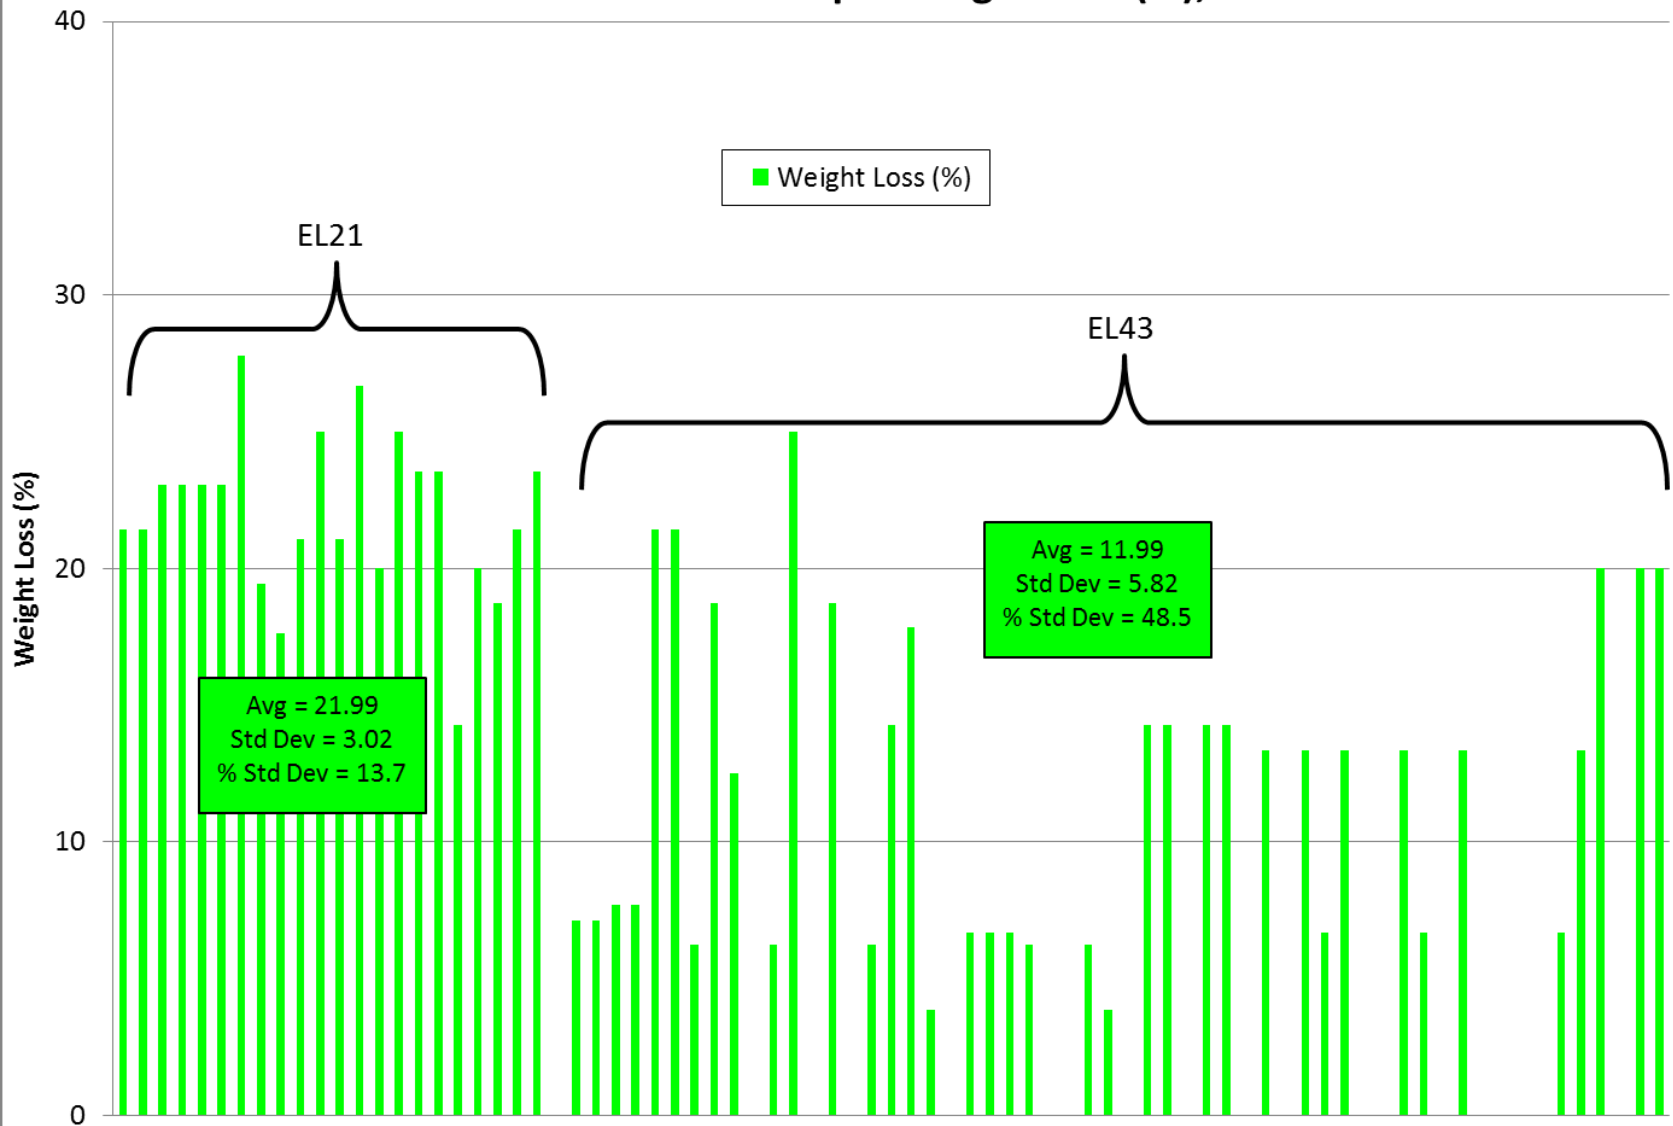


Problem: Machined Samples Do Not Lay Flat



Machined Sample Manually Manipulated



Manipulated Machined Sample Still Not Flat

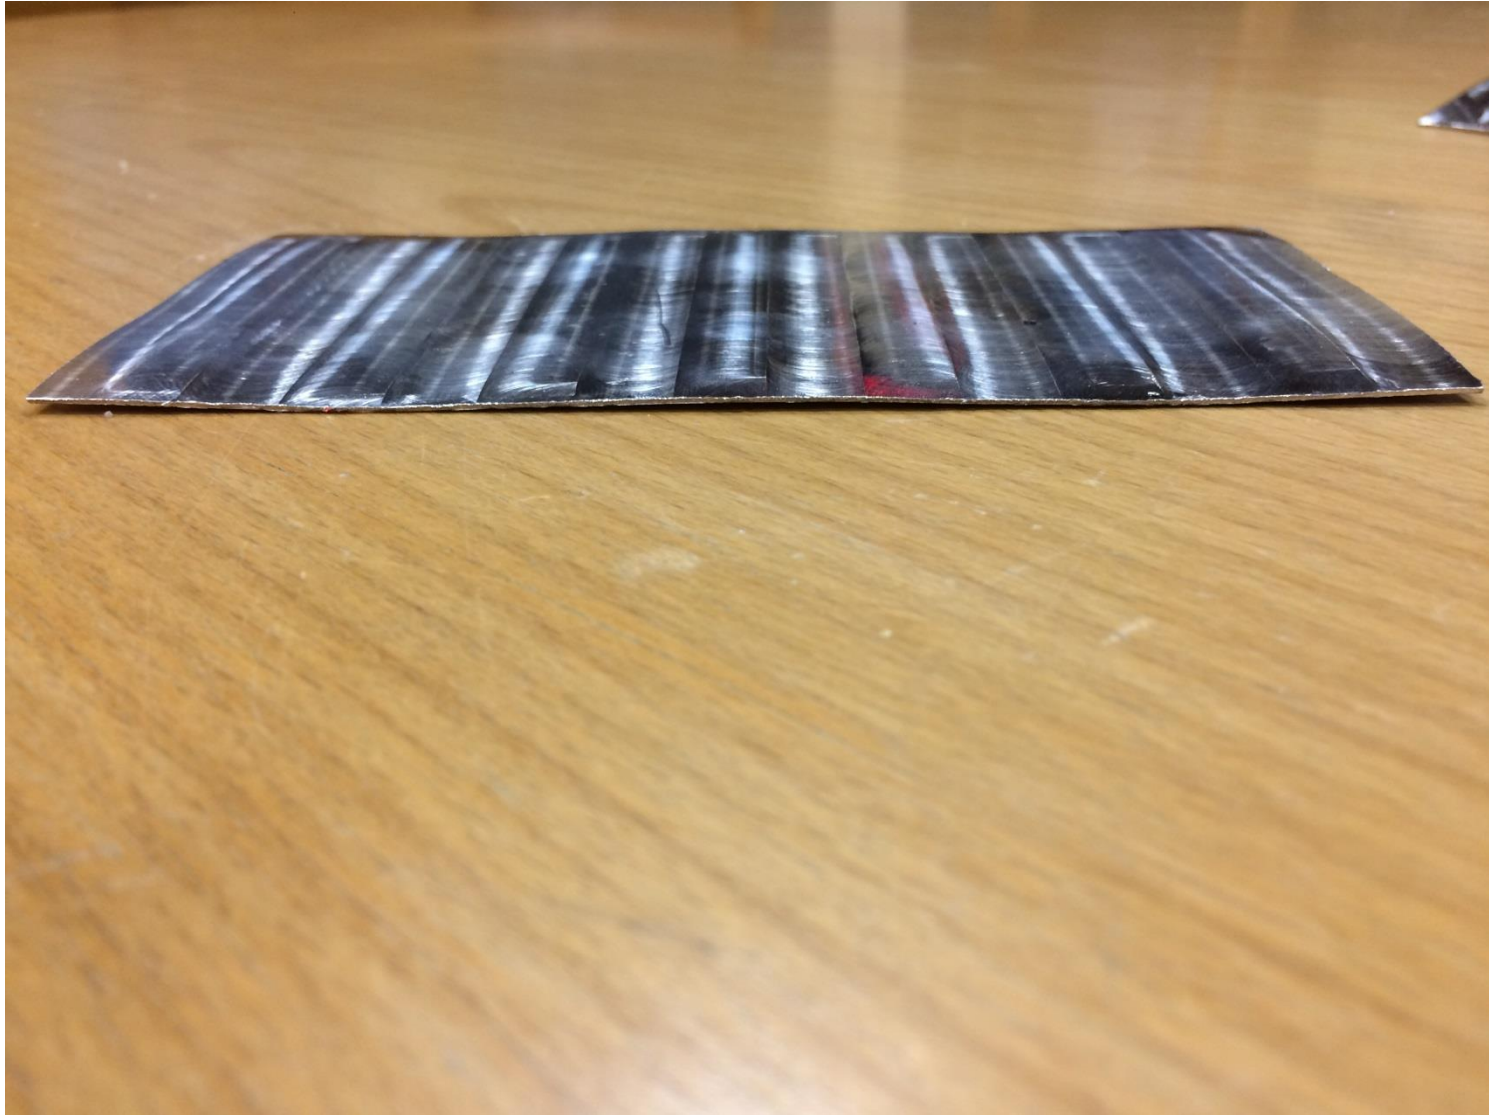


Shims Used to Raise Sample



Raised Sample Using Shims



Perimeter-Style Sample Holder

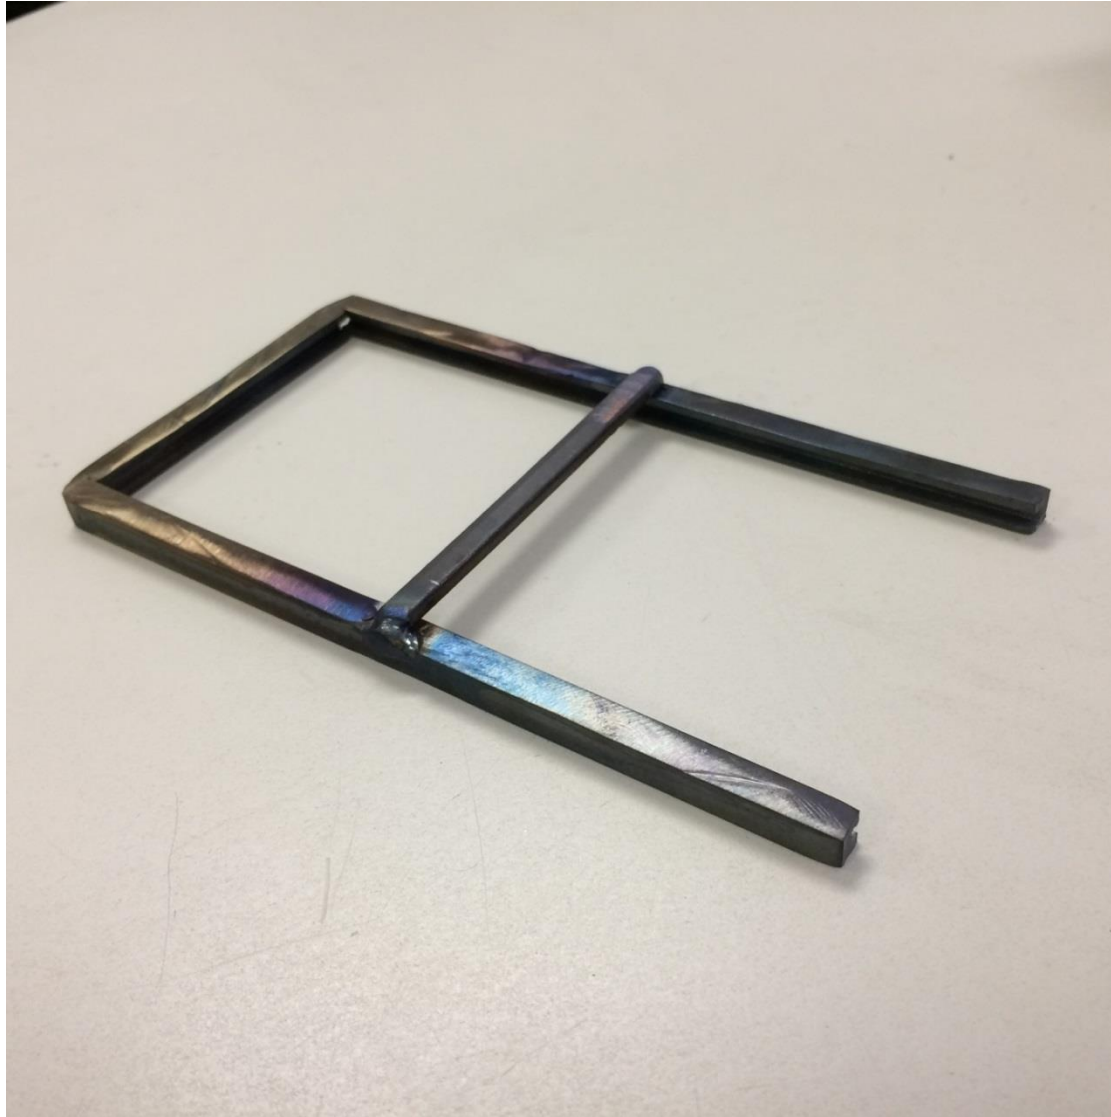


Perimeter-Style Sample Holder



Non-Conductive Perimeter-Style Sample Holder



Non-Conductive Perimeter-Style Sample Holder

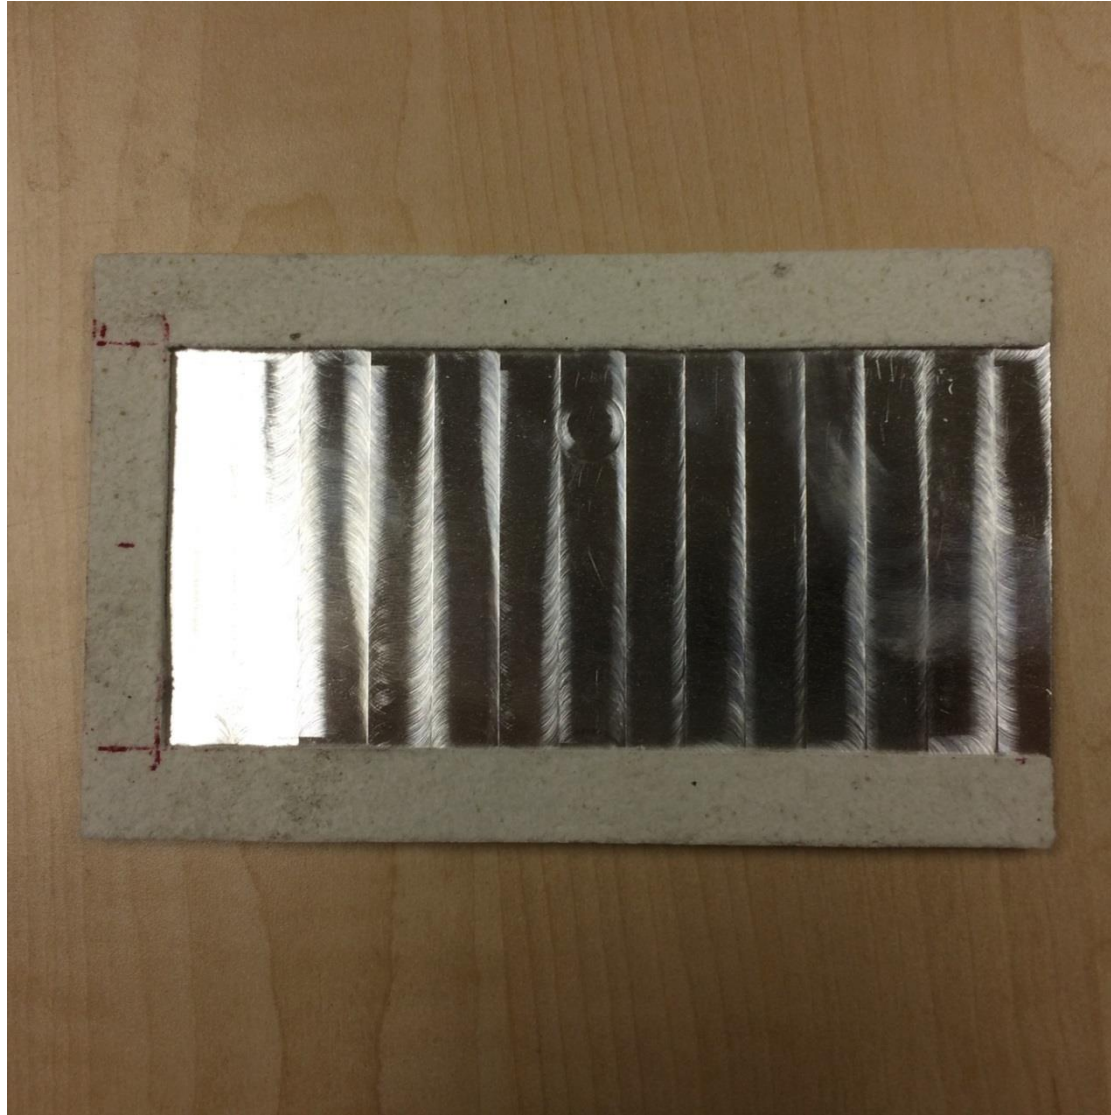

Low-Contact-Area Sample Holder, 4 Posts



Low-Contact-Area Sample Holder, 4 Posts




Low-Contact-Area Sample Holder, 4 Posts




Low-Contact-Area Sample Holder Test



Test Result, Low-Contact-Area Sample Holder

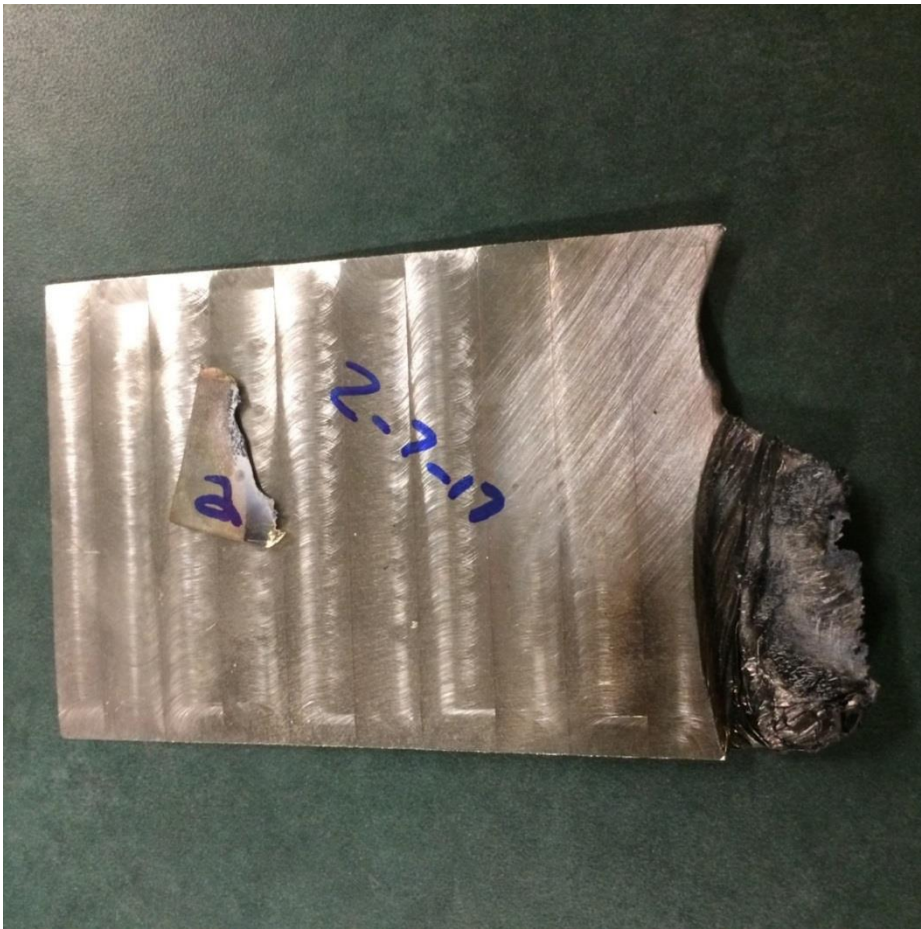

Low-Contact-Area Sample Holder, 6 Posts

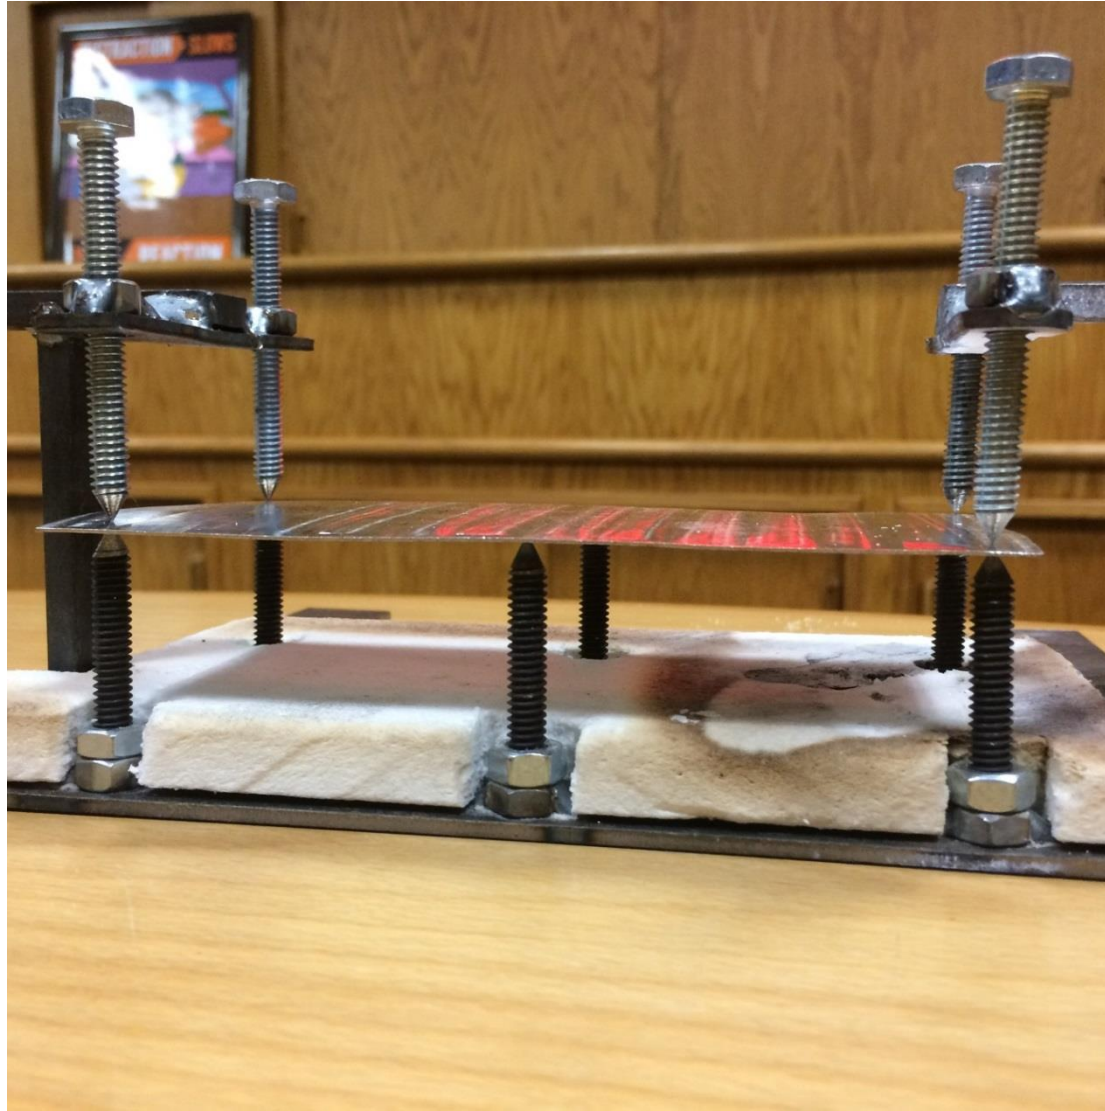


Test Result, Low-Contact-Area Sample Holder, 6 Posts



Modified Perimeter Sample Holder




Modified Perimeter Sample Holder

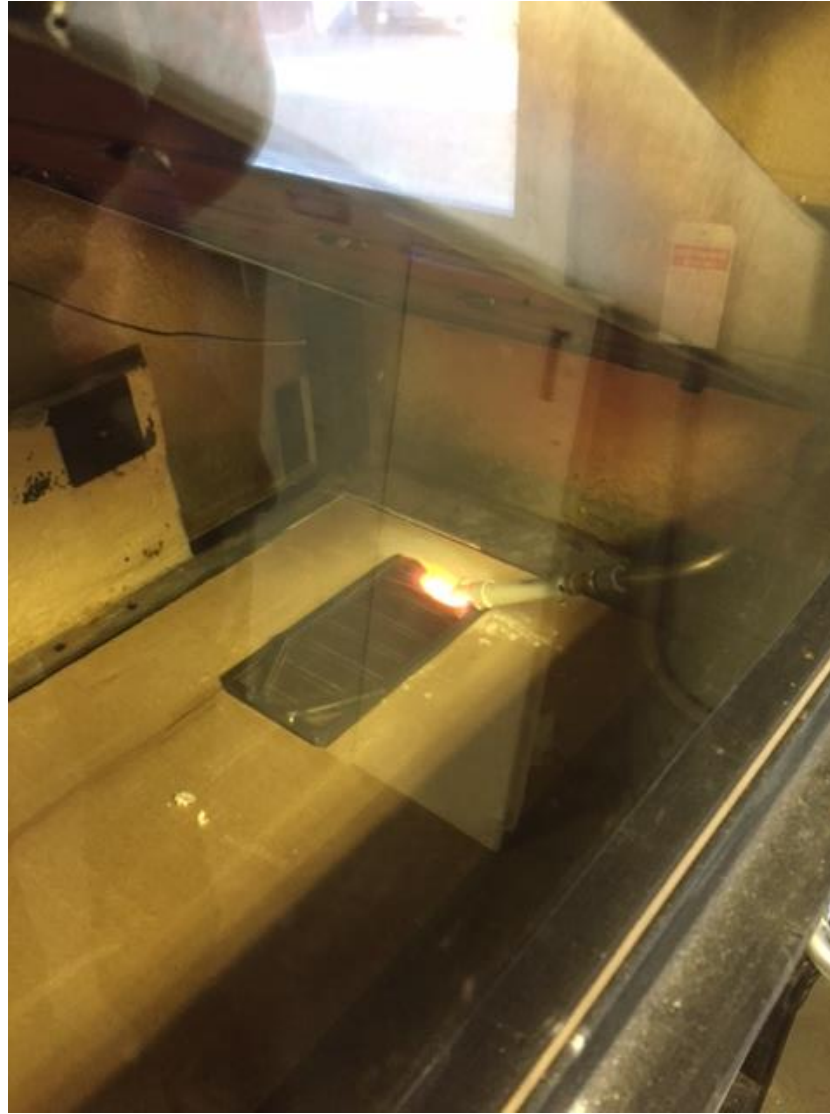


Truncated Perimeter Sample Holder



Truncated Perimeter Sample Holder

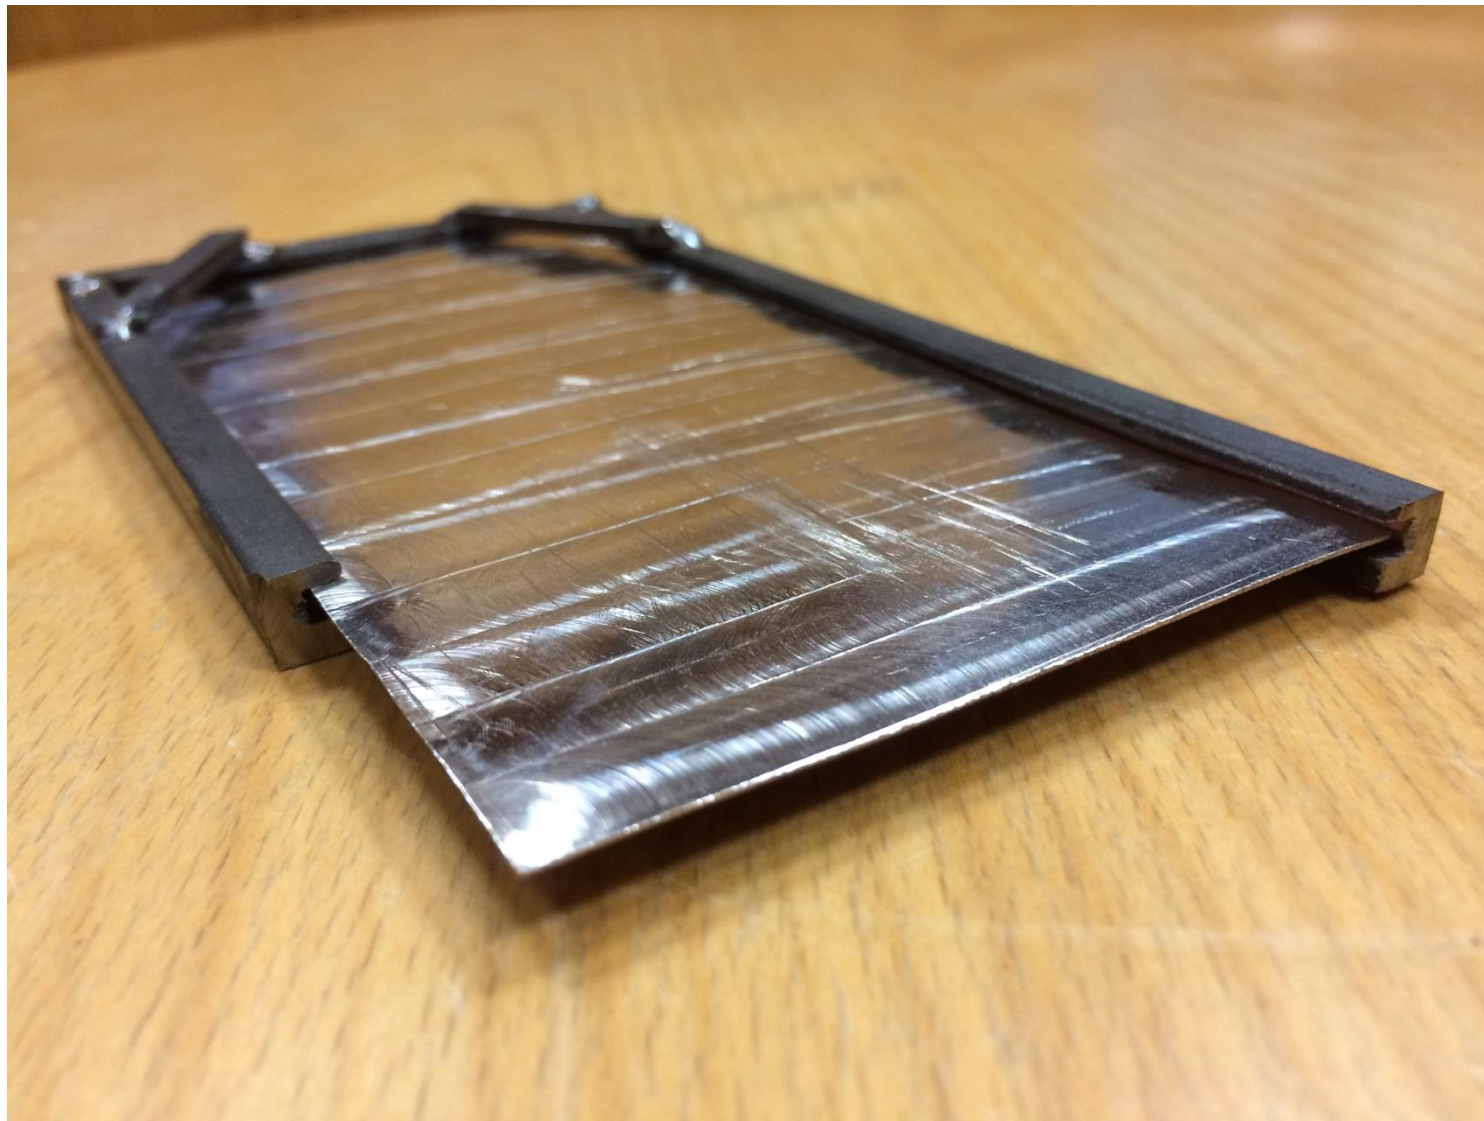


Truncated Perimeter Sample Holder

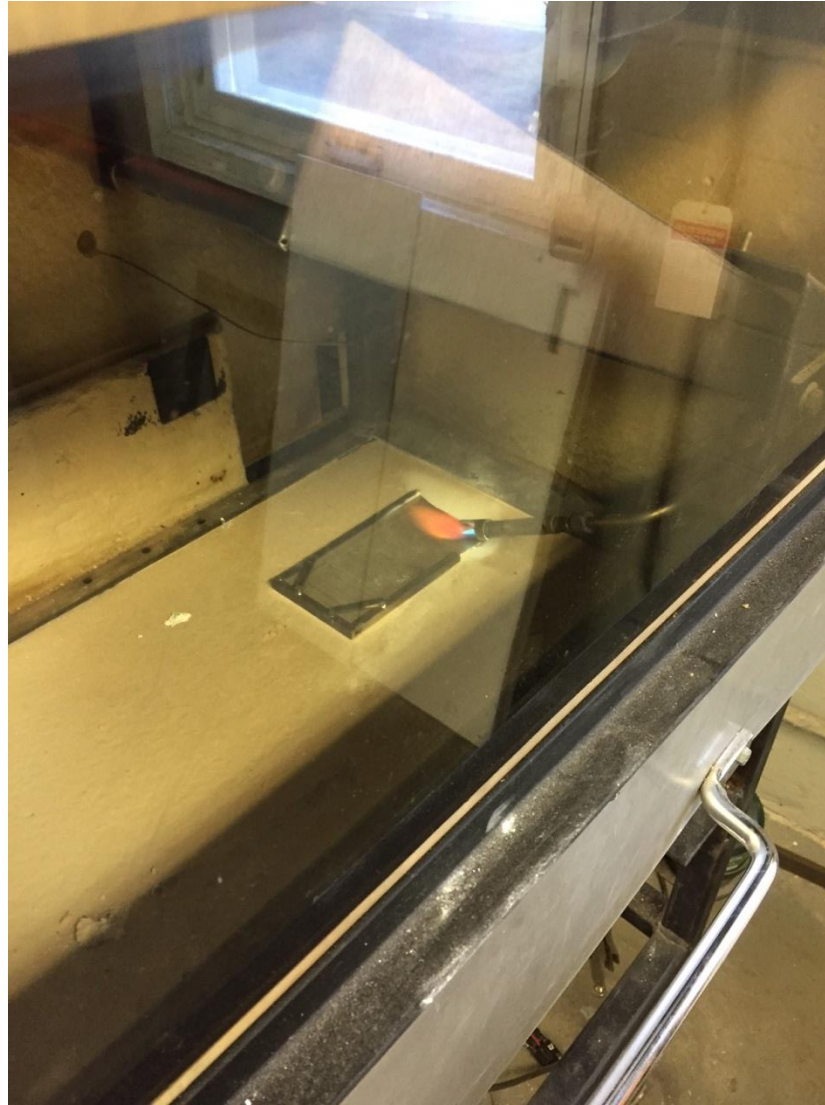


Truncated Perimeter Sample Holder



0.025-Inch Thickness, Various Sample Holders

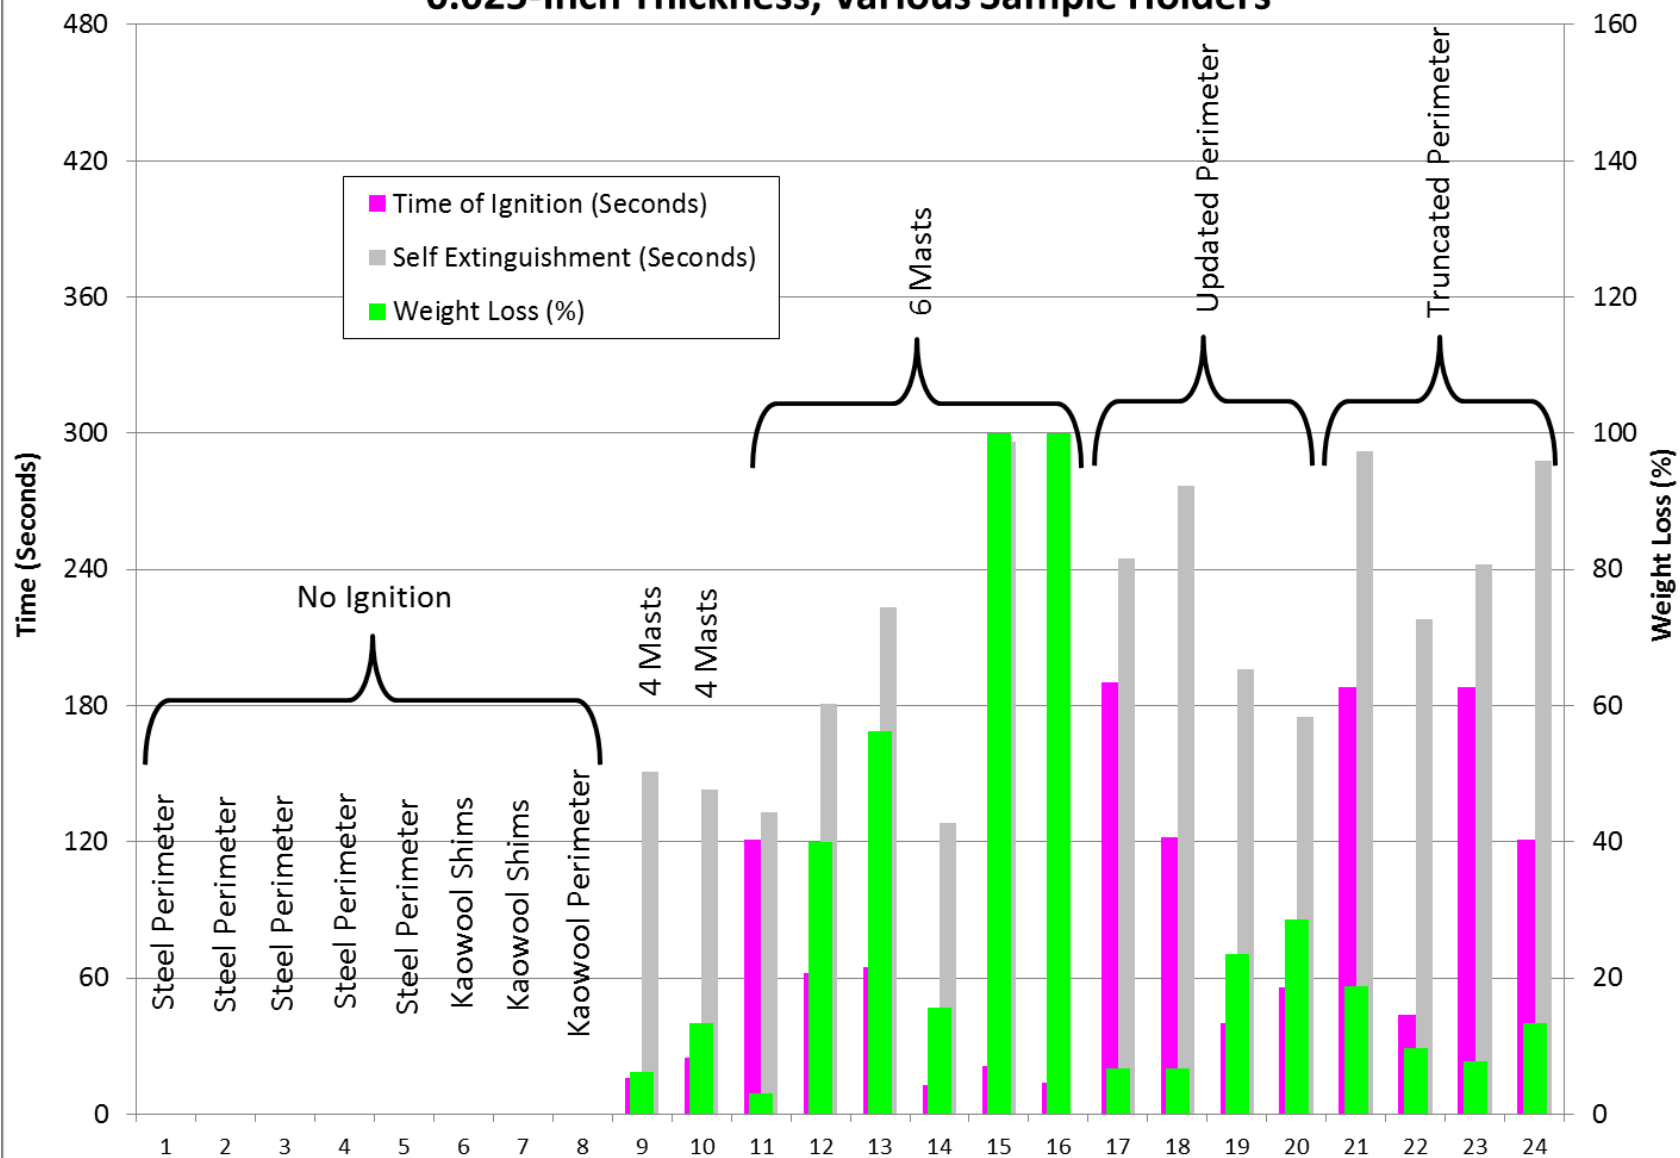

Weight Loss (%) of 0.025-Inch Thickness, Various Sample Holders

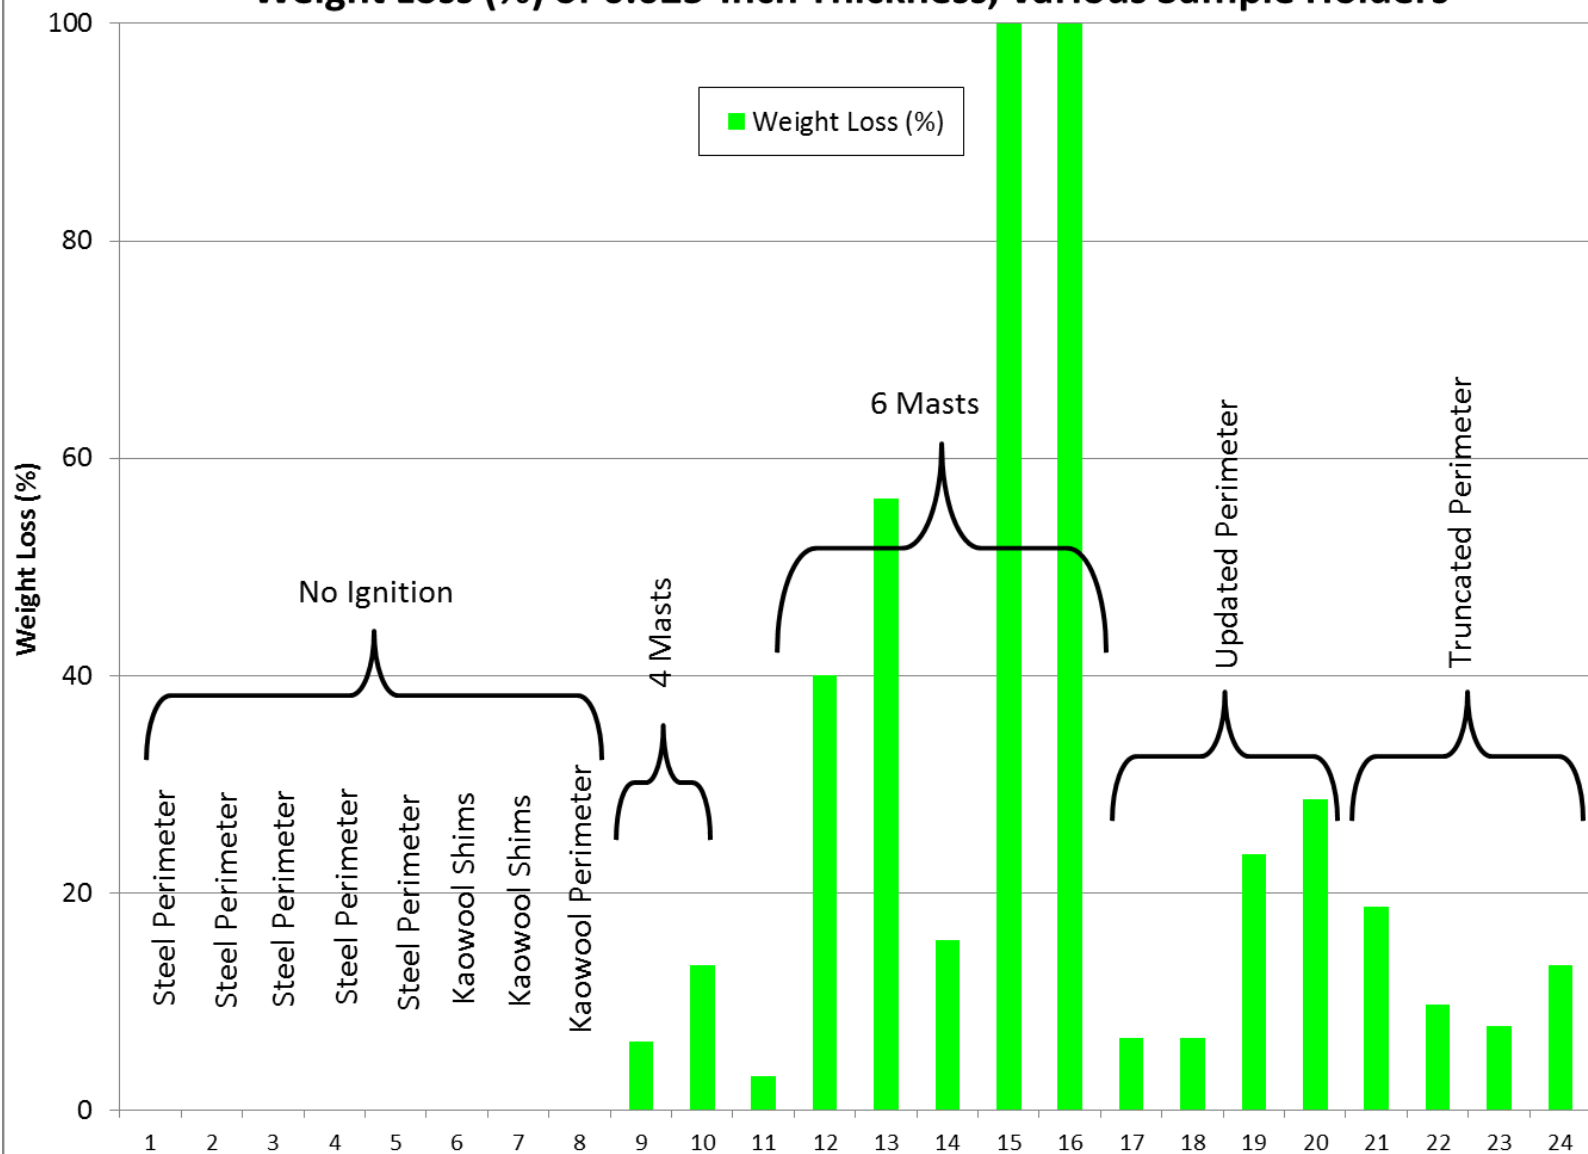

Wrap-Up, Summary, Future Work

Finalize test parameters and pass/fail criteria for magnesium alloy components located in inaccessible areas:

- *Radiant Panel Apparatus, 3- by 6-inch sample size, 0.025-inch thickness*
- *No ignition before 60 seconds (proposed)*
- *Maximum weight loss of 30% (proposed)*
- *Continue investigation of sample holder needed to prevent curling or lifting*
- *Experiment with duration of ignition (increase from 120 sec to 180 sec)*

Questions?



Chapter 25 Update

25.4.6 Sample Coatings

If a finish coating, anodizing, or other standard aerospace grade surface treatment is used on the magnesium alloy in service, it is sufficient to test the coated materials using the 12-second vertical Bunsen burner test method described in Chapter 1 of the Materials Fire Test Handbook (Vertical Bunsen Burner Test for Cabin and Cargo Compartment Materials). **Vertical Bunsen burner test samples must be fabricated with the coating applied to the magnesium alloy substrate that it will be used on in service, using the production process. The test must be conducted using a substrate thickness representative of the thinnest cross section of the in-service component. If the coating/substrate passes in this thickness (critical test configuration), the coating can be applied to any thicker in-service components of the identical magnesium alloy material without additional testing. Any in-service components having thinner cross sections will require additional vertical Bunsen burner substantiation using that coating/substrate thickness.**

Development of Advisory Circular



Potential Advisory Circular Topics


An AC on magnesium use may include some of the following:

- *Purpose*
- *Applicability*
- *Definitions*
- *Related documents*
- *Background*
- *Requirements of 25.853*
- *Compliance with 25.853*
- *Magnesium alloy flammability tests*
- *Measuring the weight of molten/re-solidified parts*
- *Determining self-extinguishment*
- *Test data collection*
- *Pass/fail criteria*
- *Engineering evaluation*




The Use of Magnesium Alloy in Cabin Areas

What is the appropriate method of test?

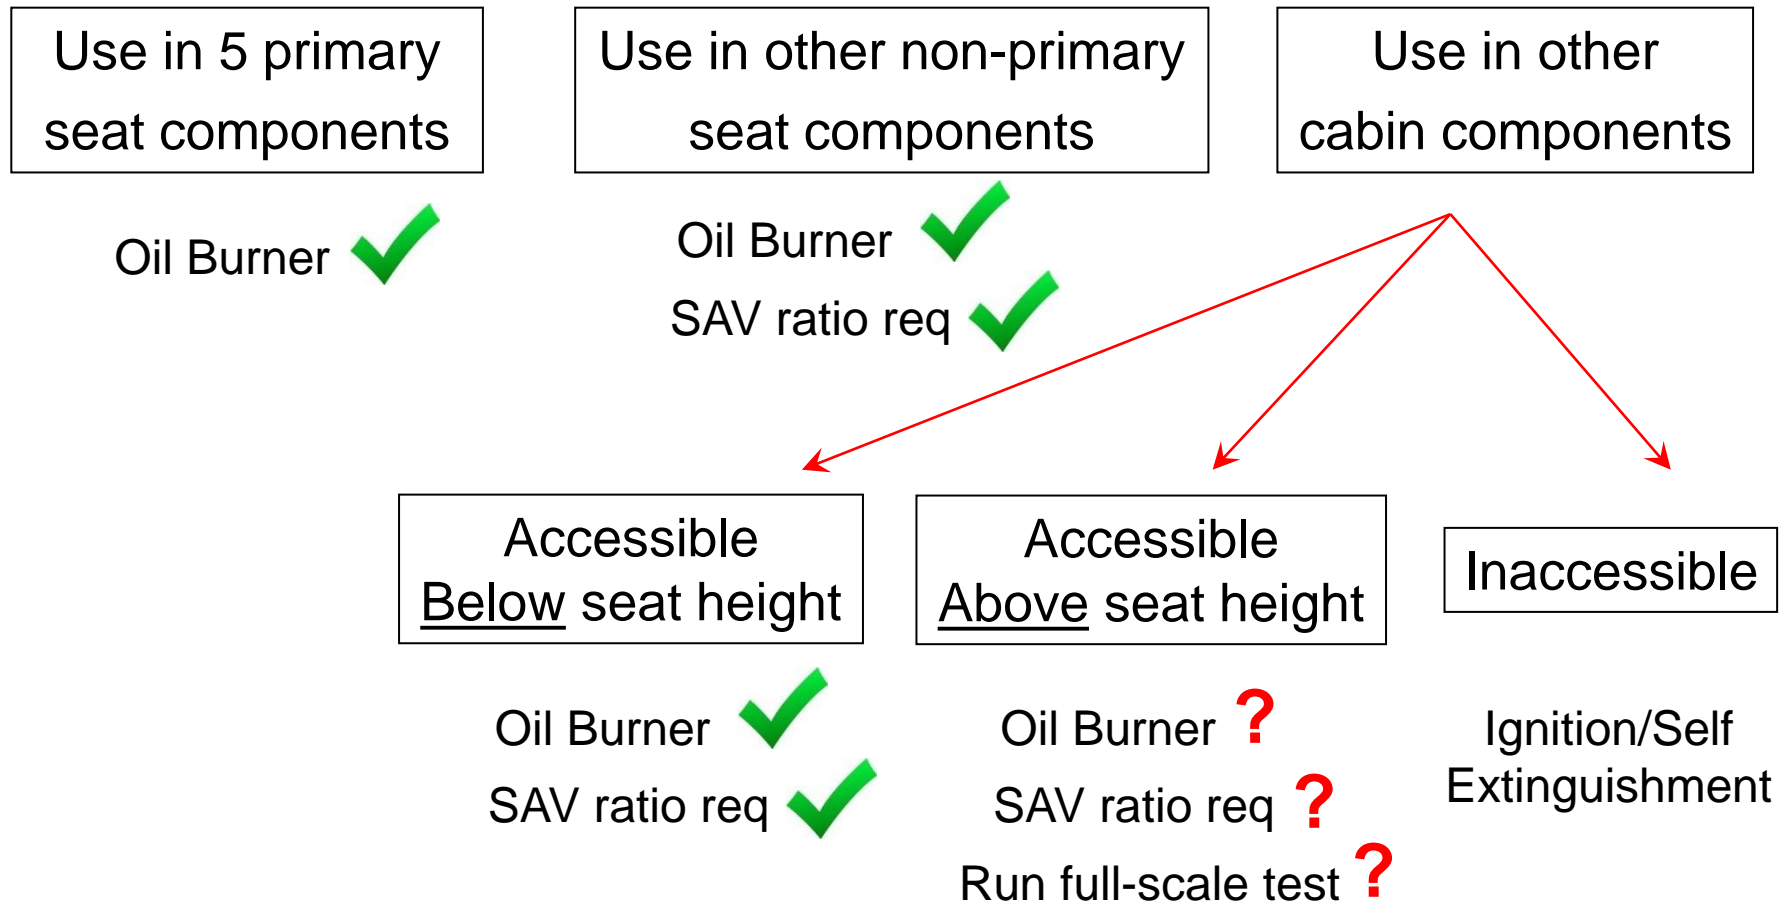

Magnesium Alloys Application in Aircraft Seat and Cabin Interiors – Installation Compliance & Approval Process

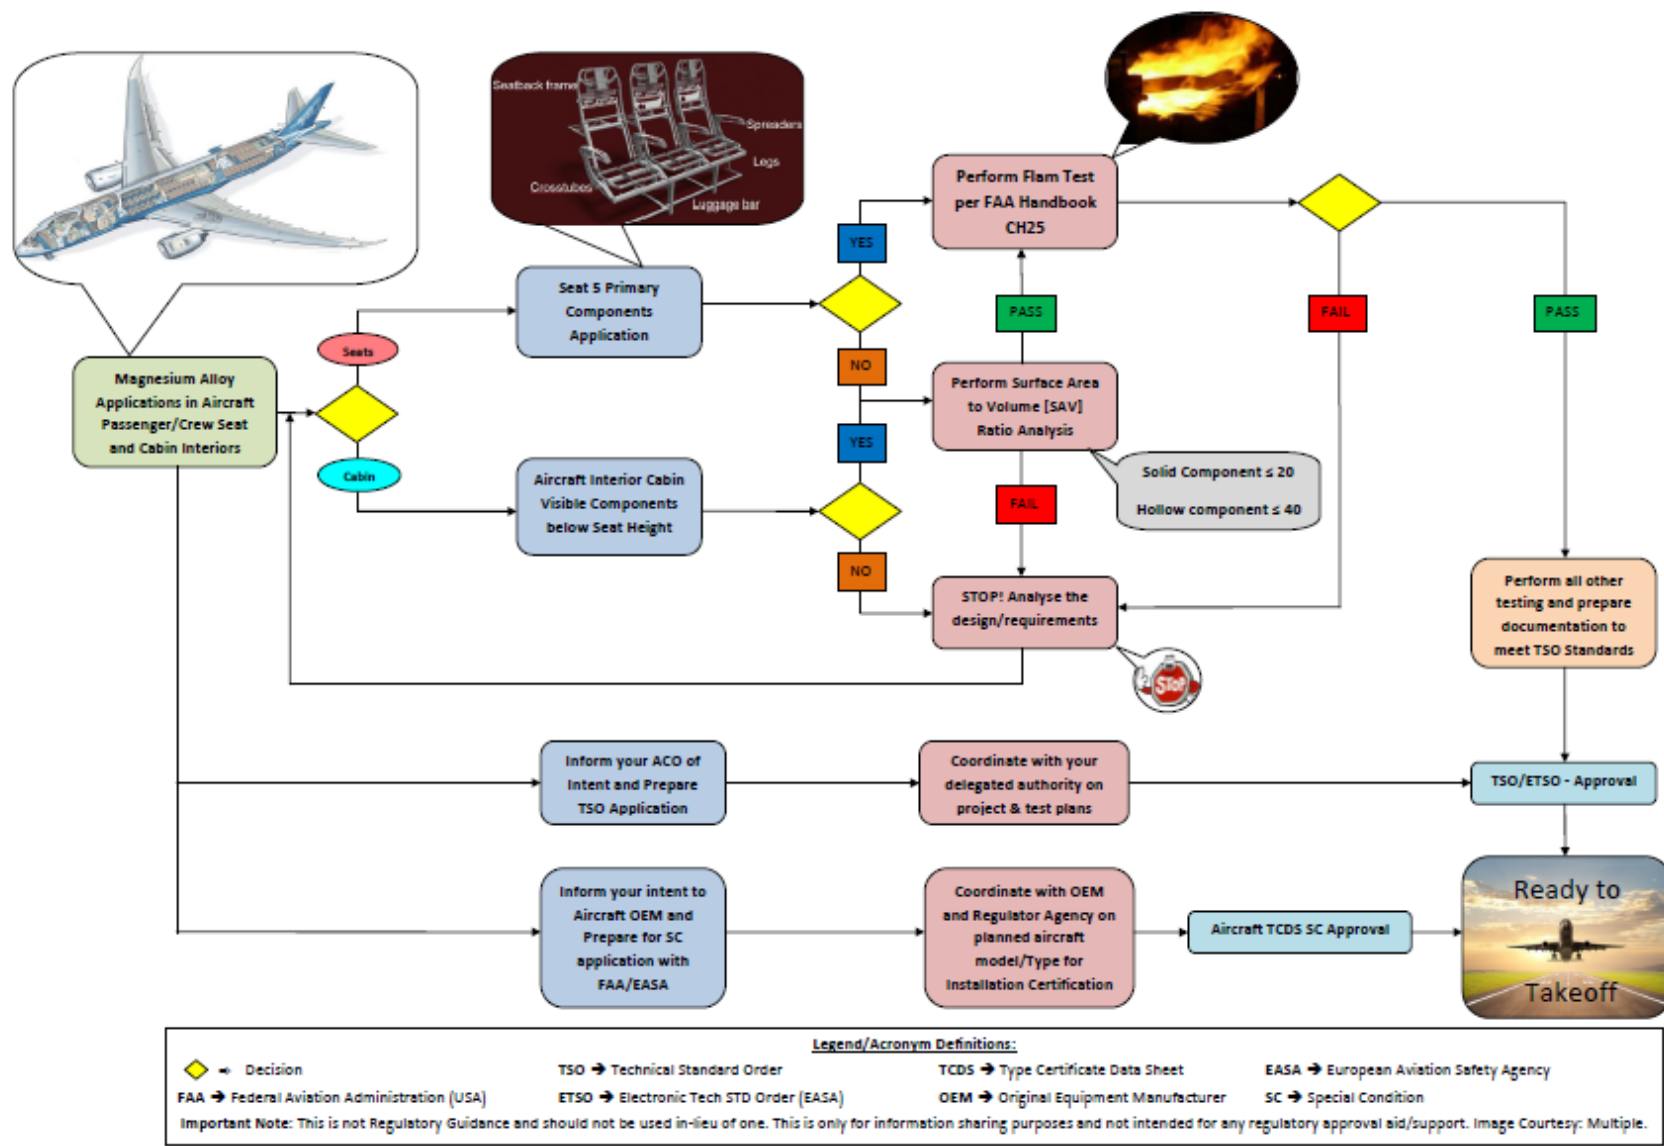

Discussion Items for Task Group

Discuss appropriate test method for magnesium alloy components located in inaccessible areas. Discuss recent testing conducted on thin samples in the radiant panel apparatus. What is impact of increasing ignition duration? What is the impact of the various sample holders on the test results. Select test and begin to finalize pass/fail criteria.

Discuss the key elements that need to be included in an Advisory Circular. For example, the appropriate method of test for each application.

Discuss the draft flowchart detailing the processes required in the certification of aircraft containing magnesium components in the passenger cabin.